

Electronic Journal of Biotechnology
EJBT-D-17-00042
Original Research Article
Received: March 9, 2017
Accepted: August 8, 2017
Areas: Food Biotechnology;

Short Title: A novel Xanthan gum

Yield and rheological properties of exopolysaccharide from a local isolate: *Xanthomonas axonopodis* pv. *vesicatoria*

Ahmet Sukru Demirci, Ibrahim Palabiyik*, Deniz Damla Altan, Demet Apaydin, Tuncay Gümüs

Department of Food Engineering, Namık Kemal University, 59030 Tekirdağ, Turkey

*Corresponding author: ipalabiyik@nku.edu.tr

Abstract

Background: The aim of the present study was to evaluate gum productivity of a local strain, *Xanthomonas axonopodis* pv. *vesicatoria* isolated from pepper plant and its rheological behavior for the first time compared to the standard strain, *Xanthomonas campestris* DSM 19000 (NRRL B-1459). The influence of operational conditions (agitation rate and inoculum volume) on gum production, and rheological properties of gums from the *Xanthomonas* strains were investigated.

Results: The isolated strain of *Xanthomonas* showed similar xanthan yield compared to the standard strain. Furthermore, this study clearly confirmed that gum yield depended on bacterial strain, agitation rate and inoculum size. The most suitable conditions for the gum production in an orbital shaker in terms of agitation rate and inoculum size were 180 rpm and 5%, respectively, resulting in an average production of 10.96 and 11.19 g/L for *X. axonopodis* pv. *Vesicatoria* and *X. campestris* DSM 19000, respectively. Regarding the rheological properties, Ostwald de Waeleand power law models were used to describe flow and oscillatory behavior of the gum solutions, respectively. Consistency of the novel gum solution remarkably was much higher than the commercial xanthan gum solution. Flow and oscillatory behavior and their temperature ramps showed that weak gel like structure could be obtained with less gum concentrations when the novel gum was used.

Conclusion: Therefore, yield and technological properties of the aqueous solutions of the exopolysaccharide synthesized by *X. axonopodis* pv. *Vesicatoria* were observed to be more suitable for industrial production.

Keywords: Agitation rate, Biodegradation, Flow behavior, Gum productivity, Gum solutions, Inoculum volume, Natural polymers, Oscillation test, Pepper plant, Xanthan yield, *Xanthomonas campestris*.

1. Introduction

It has been reported that, natural polymers such as polysaccharides have been recently the focus of interest due to their outstanding properties including biocompatibility, biodegradability, non-toxicity, and renewability [1]. Xanthan gum is an extracellular heteropolysaccharide that is produced biotechnologically by *Xanthomonas* spp. [2]. This gum authorized by the U.S. Food and Drug Administration for application as food additives without any restrictions [3].

Xanthan gum when dispersed in water quickly produces a viscous, stable solution, even at low concentrations. Due to gum pseudoplasticity, its solution in water is a suitable stabilizer, thickener, and suspending agent in many foods [4]. Today xanthan gum is the commercially most important microbial polysaccharide. Worldwide consumption of xanthan in 2014 was estimated between 150 000 and 160 000 metric tons [5].

With this respect, developing a local strain of *Xanthomonas* for xanthan production is of importance. Composition, viscosity and yield of xanthan varies depending on the *Xanthomonas* strain used in the production. Therefore, local isolates that can be used in the production of xanthan with good quality attributes should be investigated.

The commercial interest in the xanthan gum is due to its rheological properties [5]. Therefore, rheological properties and exopolysaccharide stability properties of these isolates should be investigated prior to their introduction to commercial use. The species, pathovar and strain influence of *Xanthomonas* in the rheological behavior of xanthan produced has been investigated [6,7,8,9]. Most of the previous research on microbial xanthan production has focused on the type of carbon source [10,11,12], and optimization of operating conditions [13,14].

Production parameters during fermentation process, as well as the strains used in the production, have an effect on the yield and the properties of xanthan gum [15,16].

Therefore the evaluation of these parameters for the optimization of the production of xanthan also gains importance. Potential use of these strains can be evaluated by essentially determining the optimal production parameters.

Therefore, in this study, the properties of wild-type strain of *Xanthomonas* isolated from pepper including gum rheology and xanthan gum production at different conditions of agitation rate and inoculum volume were investigated. The obtained results were compared with the the *X. campestris* DSM 19000 standard strain to evaluate the yield and the quality parameters of the gum produced using the wild-type strain of *Xanthomonas*.

2. Materials and methods

2.1. Isolation and Identification of Microorganisms

Xanthomonas axonopodis pv. *vesicatoria* was isolated from pepper (*Capsicum annuum* L) in Turkey. The identification process was carried out by conducting morphological,

biochemical, and physiological tests, including KOH solubility for Gram reactions, catalase reaction, oxidative/fermentative metabolism, and hypersensitivity to tobacco leaves. Identification of the strain was confirmed by fatty acid methyl ester (FAME) analysis [17,18].

Xanthomonas campestris DSM 19000 (NRRL B-1459), which is the standard bacterium, was obtained from the Leibniz Institute DSMZ - German Collection of Microorganisms and Cell Cultures (Germany).

2.2. Culture media

- A) The organisms were maintained in YM (Yeast Malt) agar containing (gL⁻¹): 3.0 yeast extract; 3.0 malt extract; 5.0 peptone; 10.0 glucose; 20.0 agar and distilled water (pH 7.2) [19]. To verify some morphological characteristics, the strains were transferred every 14 days and stored at $\pm 4^{\circ}\text{C}$.
- B) Cell production was carried out in two stages. In the first stage, a pre-inoculum was prepared using YM agar and incubated at $28 \pm 2^{\circ}\text{C}$ for 24-48 h until the optical density value at 560 nm reached 3-4 ($\text{OD}_{560} = 3-4$). The inoculum was inoculated in 50 mL YM broth and incubated at $28 \pm 2^{\circ}\text{C}$ and 180 rpm. Then, 2 mL aliquot of the pre-inoculum was taken aseptically to an Erlenmeyer flask containing 100 mL of YM broth and incubated again at $28 \pm 2^{\circ}\text{C}$ and 180 rpm. The cells were produced using a pre-inoculum upto about 10^8 (cfu) mL⁻¹ cell concentration.
- C) The xanthan gum production medium comprised 40.0 (g/L) glucose, 2.1 (g/L) citric acid, 2.866 (g/L) KH_2PO_4 , 0.507 (g/L) MgCl_2 , 0.089 (g/L) Na_2SO_4 , 0.006 (g/L) H_3BO_3 , 0.006 (g/L) ZnO , 0.020 (g/L) $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$, 0.020 (g/L) CaCO_3 . The carbon source used for the fermentation studies was glucose [20].

2.3. Xanthan gum production

Yield and viscosity values in xanthan varies depending on microbial strains, colonial variation, media and the parameters of the fermentation process to obtain the biopolymer [7]. Two process conditions, agitation rate and inoculum volume were assessed in this study. Xanthan gum was produced using a 1000 mL Erlenmeyer flasks with 500 mL medium. It has been reported that the optimum temperature, fermentation period and initial pH parameters were 28°C , 72 h and pH 7.2, respectively [21]. In accordance with the results reported in the previous studies, the system temperature was maintained at 28°C using a temperature controlled orbital shaker incubator. This procedure was essential as the substrate consumption reactions were exothermic and therefore the temperature of the medium tended to rise. The initial pH of the fermentation medium was 7.2, however, constant pH control was not possible in the shaker. The agitation rate (180-300 rpm) and inoculum size (5 and 10%) levels were studied and the productivity of the 2 microorganisms by fermentation was compared with the variable fermentation conditions. All experiments were performed triplicate. The medium used for fermentation was centrifuged 30 min for cell separation (SIGMA 2-16KL) at 4°C and 10,000 rpm. Isopropanol (Merck) was added to the supernatant in 1:3 ratio (v/v) for the recovery of the biopolymer. The obtained polymer was dried at 50°C

until reaching constant weight. Then, the dried polymer was ground in a disk mill until the granule size reached 0.5 μm . The evaluation of the biopolymers of each strain at different conditions was performed by weighing the the dry product per liter of fermented broth. The average values were determined in gL^{-1} .

2.4. Rheological behaviors

The rheological behaviors were determined using three concentrations frequently used in food systems (0.5%, 1%, and 2%). Samples were prepared by dissolving the desired amount of dry sample in deionized water with a magnetic stirrer at 40°C. Prepared samples were tempered for 24 h at room temperature before conducting any experiment. Reproducibility of the data was checked by repeating experiments between 3 and 5 times with new samples. Rheological analyses were conducted by suitable models to quantify the properties of xanthan gums.

2.4.1. Steady shear measurements

A controlled stress Discovery Hybrid Rheometer-2 (TA Instruments New Castle, DE, USA) fitted with a parallel-plate geometry (stainless steel, 40 mm diameter, 1000 μm gap) was used for the determination of rheological properties. The shear rate range adopted for xanthan solutions at 0.5, 1 and 2 wt % was 1-100 s^{-1} . Shear rate, shear stress, normal force, torque and apparent viscosity data were collected during the trials. To determine the flow behaviors of the samples, Ostwald de Waele model was used, as follows:

$$\sigma = K(\dot{\gamma})^n \quad \text{[Equation 1]}$$

where σ is the shear stress (Pa), K is the consistency coefficient ($\text{Pa}\cdot\text{s}^n$), $\dot{\gamma}$ is the shear rate (s^{-1}), and n is the flow behavior index (dimensionless).

2.4.2. Dynamic Rheological Measurements

Dynamic oscillatory shear rheometer Discovery Hybrid Rheometer-2 (TA Instruments New Castle, DE, USA) was used to conduct stress sweep and frequency sweep tests for all gum solution. Stress sweep test was used for the determination of linear viscoelastic region. Frequency sweep test was performed at 0.6 Pa over a frequency range of 0.05-100 rad/s. The following power law was used for the modeling of the elastic or storage modulus (G') and the viscous or loss modulus (G''):

$$G' = K'(\omega')^n \quad \text{[Equation 2]}$$

$$G'' = K''(\omega'')^n \quad \text{[Equation 3]}$$

where K' , ω' and n' were intercepts, angular frequency and elastic behavior index, respectively and K'' , ω'' and n'' were viscous counterparts.

2.4.3. Effect of Temperature on the Rheological Parameters

The effect of temperature on viscosity of the gum solutions was also investigated and modeled by Arrhenius equation [22].

$$A = A_0 \exp(E_a/RT)$$

[Equation 4]

where A is the parameter (Pa.s), A_0 is the constant of Arrhenius equation (Pa.s), E_a is the activation energy (kJ/mol), R is gas constant ($8,314 \times 10^{-3}$ kJ/molK), and T is temperature (K).

2.5. Statistical Analysis

The results were statistically analyzed using Minitab for Windows Release 14®. The Duncan's multiple range test was used for the calculation of standard errors.

3. Results and Discussion

3.1. Xanthan yield

Many studies have reported that the strain used in the production of Xanthan had an effect on the xanthan yield and its properties [23,24]. The effects of the parameters for the *X. axonopodis* pv. *vesicatoria* and *X. campestris* DSM 19000 in terms of xanthan gum production are presented in **Figure 1**. Both inoculum volume and agitation rate were shown to be significant factors for xanthan production.

The highest xanthan gum yield values were determined in 180 rpm agitation rate and 5% inoculum volume in broth for both *X. axonopodis* pv. *vesicatoria* and *X. campestris* DSM 19000 with 10.96 and 11.19 gL^{-1} , respectively. Generally, isolate of *X. axonopodis* pv. *vesicatoria* presented remarkable and similar xanthan gum yields compared to standard strain in the all experiments.

The previous studies [6,7,25,26,27,28] have reported that the strain had an effect on the production. The results obtained in the present study confirmed these reported results. It was concluded that the first step in the studies on xanthan production with the highest yield should be the selection of strain.

Regarding the effect of inoculum volume as can be seen from **Figure 1**, it was shown that higher yields were obtained at 5% inoculum in all agitation rates except 300 rpm. The inoculum volume 10% facilitated better the production of biomass rather than byproduct, xanthan. Especially, for *X. axonopodis* pv. *vesicatoria*, increasing inoculum volume in the medium stimulated the xanthan production dramatically and nearly halved gum production from 5% to 10%. These results showed that the increase in cell

concentration had no effect on the increase in xanthan production. Ben Salah et al. [29] have reported that the optimum inoculum size for maximum xanthan production using *X. campestris* was 5%. The results obtained in the present study were in line with those obtained by the researchers. Higher amounts of inoculum possibly had no positive effect on the yield as the nutrients and the space for them was not sufficient for an active growth. The size of the inoculum can change depending on the strain type. Fernandes-Silva et al. [30], in their study, produced xanthan using cheese whey as substrate in fermentation. The researchers adopted 20% (v/v) 24 h inoculum for production.

As seen in **Figure 1**, agitation, in general, had a significant effect on xanthan production as the xanthan yield increased as the agitation values decreased, except for 300 rpm. However, some researchers reported that higher stirrer speed is necessary for xanthan production by *X. campestris* [31], *X. campestris* ATCC 1395 [32], *X. campestris* ATCC 33913 [33], *X. campestris* pv. *mangiferaeindicae* IBSBF 1230 [19], *X. arboricola* pv *pruni* 106 [34], *X. campestris* PTCC 1473 [35]. Nevertheless, our results were in agreement with that of Ben Salah et al. [29] who evaluated xanthan production at distinct stirrer speeds (50, 180 and 250 rpm) and obtained highest levels of xanthan gum at an agitation speed of 180 rpm. Ben Salah et al. [29] have reported that lower xanthan gum values were associated with the bacterial fragmentation mediated by mechanical shearing. According to the results, it can be speculated that depending on the operational conditions there is an optimum mixing rate which does not cause bacterial damage and at the same time does not limit mass transfer. Generally, microorganism investigated in this study did not resist high agitation probably due to vulnerable cell structure against hydrodynamic stresses. These results confirm that yield depended on operational conditions and bacterial strain.

3.2. Rheological properties of xanthan gums

3.2.1. Steady shear properties

The gums produced by both microorganisms were also evaluated rheologically. **Figure 2** showed that the samples had a pseudoplastic behavior, resulting in an apparent decrease in viscosity with the increase in shear rate. Generally, solutions of exopolysaccharides obtained from microorganisms showed this kind of behavior [19,31]. At all gum concentrations of the solutions, gum from the local strain (*X. axonopodis* pv. *vesicatoria*) remarkably showed higher viscosity than the commercial xanthan gum obtained from standard strain (*X. campestris* DSM 19000). Ostwald de Waele model was used to fit experimental viscosity versus shear rate data to make comparison of non-Newtonian behavior of the solutions and could be seen in **Table 1**. R^2 values were higher than 0.98 indicating good fitting of the model. As could be seen from K (consistency index) values, gum from *X. axonopodis* pv. *vesicatoria* formed solutions at higher viscosity at all concentrations. However, n (flow behavior index) was lower compared to standard strain indicating low stability against shear. Therefore, when shear rate increased, more pronounced decrease was obtained for gum solution from *X. axonopodis* pv. *vesicatoria*. In one of the study investigated one hundred fifty wild strains of *Xanthomonas*, *Xanthomonas campestris* ICa-125 strain isolated from cabbage showed lower viscosity than the standard strain [36].

Concerning the effect of temperature on the viscosity values of gum solutions at 10 s^{-1} shear rate, generally decrease was observed as expected in **Figure 3**. Increasing the gum concentration of the solutions led to sharp decrease in the viscosity values with temperature increase. Arrhenius model was used to compare viscosity change of solutions with respect to temperature. R^2 values were found between 0.96 and 0.99 in **Table 1**. It was clearly seen that activation energies changed between 6 and 25 kJ/mol. Concentration increase resulted in decrease in activation energies as expected for xanthan gum solutions [37]. Similar temperature stability of the gum solutions except for 1% gum concentrations was observed due to similar activation energies for both gums.

3.2.2. Dynamic rheological properties

Regarding the viscoelastic properties of gum solutions, **Figure 4** showed oscillatory frequency sweep tests in linear viscoelastic regions of the studied gums. Storage (G') and loss (G'') modulus values increased with gum concentrations due to increase in the interaction between biopolymer molecules. These values also increased with angular frequency showing dominance of elastic response at higher frequencies. The solutions of both type of xanthan gums demonstrated weak-gel behavior as both G' and G'' values as well as the difference between them increased with polymer concentration. However, crossover frequency was observed at the 1% and 0.5% concentration of gum from *X. campestris* DSM 19000 and 0.5% of *X. axonopodis* pv. *vesicatoria* indicating the occurrence of macromolecular entanglements strengthened by intermolecular and intramolecular hydrogen bonds [38]. At 0.5% concentration both gums showed viscous nature as loss modulus was lower than the storage modulus. However solution with 1% gum concentration from *X. axonopodis* pv. *vesicatoria* showed elastic nature unlike gum from *X. campestris* DSM 19000 which indicated higher gel forming capacity of the novel type of xanthan gum. At 2% concentration, viscoelastic behavior of the xanthan gum solutions was dominated by elastic nature and G' and G'' values of novel gum was higher than that of standard xanthan gum.

Oscillatory behavior of the solutions was also modeled according to power law and the corresponding viscoelastic parameters were shown in **Table 2**. *X. axonopodis* pv. *vesicatoria* showed weak gel-like behavior at all studied concentration as the slopes ($n' = 0.32-2.95$; $n'' = 0.18-3.62$) were positive and values of K' ($4.1 \cdot 10^{-5}-18$) were much higher than those of K'' ($2 \cdot 10^{-6}-11$) [39]. However, commercial xanthan obtained from *X. campestris* DSM 19000 only demonstrated weak gel-like behavior at high concentration (2%). At 0.5% concentration both gums showed fluid-like behavior as the value of the exponents describing the dependence of moduli with frequency, being higher than unity [40].

Figure 3 indicated the comparison of temperature dependence of G' and G'' between both xanthan gums. Remarkably from 6 to 60°C, G' and G'' values of novel xanthan gum solution from *X. axonopodis* pv. *vesicatoria* were always higher than that of the standard xanthan gum solution. Therefore, temperature stability of oscillatory behavior of the novel gum was also proved.

4. Conclusion

Due to wide applications of xanthan gum, it becomes important to develop a local strain of *Xanthomonas* which can produce polysaccharide with high yield and technological properties. In this study, similar xanthan yields were obtained for local isolate of *X. axonopodis* pv. *vesicatoria* compared to standard strain. Bacterial strain, agitation rate and inoculum size was shown to affect gum yield. For both strains, the best agitation rate and inoculum size conditions for the production of xanthan in an orbital shaker were found to be 180 rpm and 5 %, respectively, which results in an average production of 10.96 and 11.19 g/L for *X. axonopodis* pv. *vesicatoria* and *X. campestris* DSM 19000, respectively. Increase in inoculum size and agitation rate lowered xanthan yield for both microorganisms. Concerning the steady shear properties, Ostwald de Waele model was used to make comparison of non-Newtonian behavior of the solutions and consistencies of solutions belonging to *X. axonopodis* pv. *vesicatoria* were higher at all concentrations. Arrhenius model was used to compare viscosity change of solutions with respect to temperature. Similar activation energies for both gum solutions indicated comparable temperature stability of the novel gum with the commercial xanthan gum. Regarding the viscoelastic properties of gum solutions, power law was used to model dynamic oscillatory behavior of the solutions. Solutions belonging to *X. axonopodis* pv. *vesicatoria* showed weak gel-like behavior at all studied concentration whereas commercial xanthan obtained from *X. campestris* DSM 19000 only demonstrated this behavior only at high concentration (2%). Therefore, the results clearly indicated the better technological properties of the new gum synthesized from *X. axonopodis* pv. *vesicatoria* and comparable yield values of both gums confirmed the suitability of industrial production of this novel gum. Further work will focus mainly on the chemical characterization of the polymer as well as on purification and clarification methods.

Financial support

We thank The Scientific and Technological Research Council of Turkey (TUBITAK) for financial support (Project Number TOVAG-114O429)

References

- [1] Zia KM, Zia F, Zuber M, et al. Alginate based polyurethanes: A review of recent advances and perspective. *Int J Biol Macromol* 2015;79:377-387. DOI: <http://dx.doi.org/10.1016/j.ijbiomac.2015.04.076>
- [2] Niknezhad SV, Asadollahi MA, Zamani A, et al. Production of xanthan gum by free and immobilized cells of *Xanthomonas campestris* and *Xanthomonas pelargonii*. *Int J Biol Macromol* 2016;82:751-756. DOI: <https://doi.org/10.1016/j.ijbiomac.2015.10.065>
- [3] Ghashghaei T, Soudi MR, Hoseinkhani S. Optimization of xanthan gum production from grape juice concentrate using Plackett-Burman design and response surface methodology. *Appl Food Biotechnol* 2016;3:15-23.
- [4] Niknezhad SV, Asadollahi MA, Zamani A, et al. Optimization of xanthan gum production using cheese whey and response surface methodology. *Food Sci Biotechnol* 2015;24(2):453-460 DOI: <http://dx.doi.org/10.1007/s10068-015-0060-9>

- [5] Hublik G. In: Moeller M, Matyjaszewski K, editors. Polymer Science: A Comprehensive Reference. Elsevier Inc; 2012, p. 221-229. DOI: <http://dx.doi.org/10.1016/B978-0-12-803581-8.01529-0>
- [6] Nitschke M, Thomas RWSP. Xanthan gum production by wild-type isolates of *Xanthomonas campestris*. World J Microb Biot 1995;11(5):502-504 DOI: <http://dx.doi.org/10.1007/BF00286361>
- [7] Moreira AS, Vendruscolo JLS, Gil-Tunes C, et al. Screening among 18 novel strains of *Xanthomonas campestris* pv pruni. Food Hydrocolloid 2001;15(4-6):469-474 DOI: [https://doi.org/10.1016/S0268-005X\(01\)00092-3](https://doi.org/10.1016/S0268-005X(01)00092-3)
- [8] Rottava I, Batesini G, Silva MF, et al. Xanthan gum production and rheological behavior using different strains of *Xanthomonas* sp. Carbohydr Polym 2009;77(1):65-71 DOI: <https://doi.org/10.1016/j.carbpol.2008.12.001>
- [9] Li P, Li T, Zeng Y, et al. Biosynthesis of xanthan gum by *Xanthomonas campestris* LREL1-1 using kitchen waste as the sole substrate. Carbohydr Polym 2016;151:684-691 DOI: <http://dx.doi.org/10.1016/j.carbpol.2016.06.017>
- [10] Kalogiannis S, Iakovidou G, Liakopoulou KM, et al. Optimization of xanthan gum production by *Xanthomonas campestris* grown in molasses. Process Biochem 2003;39(2):249-256 DOI: [https://doi.org/10.1016/S0032-9592\(03\)00067-0](https://doi.org/10.1016/S0032-9592(03)00067-0)
- [11] Jazini MH, Fereydouni E, Karimi K. Microbial xanthan gum production from alkali-pretreated rice straw. RSC Adv 2017;7(6):3507–3514 DOI: <https://doi.org/10.1039/C6RA26185J>
- [12] Ben Salah R, Chaari K, Besbes S, et al. Optimisation of xanthan gum production by palm date (*Phoenix dactylifera* L.) juice by-products using response surface methodology. Food Chem 2010;121(2):627-633 DOI: <https://doi.org/10.1016/j.foodchem.2009.12.077>
- [13] Zhao Z, Zhou C, Zhang X, et al. Optimization and kinetics analysis of xanthan gum wastewater treatment with pyrolusite. Env Prog Sust En 2014;33(2):430-436 DOI: <https://doi.org/10.1002/ep.11802>
- [14] Faria S, Vieira PA, Resende MM, et al. Application of a model using the phenomenological approach for prediction of growth and xanthan gum production with sugarcane broth in a batch process. LWT Food Sci Technol 2010;43(3):498-506 DOI: <https://doi.org/10.1016/j.lwt.2009.09.018>
- [15] García-Ochoa F, Santos VE, Casas JA, et al. Xanthan gum: production, recovery, and properties. Biotechnol Adv 2000;18(7):549-579. DOI: [http://dx.doi.org/10.1016/S0734-9750\(00\)00050-1](http://dx.doi.org/10.1016/S0734-9750(00)00050-1)
- [16] Lopez M., Vargas-Garcia MC, Suarez-Estrella F, et al. Properties of xanthan obtained from agricultural wastes acid hydrolysates. J Food Eng 2004;63(1):111-115. DOI: [http://dx.doi.org/10.1016/S0260-8774\(03\)00289-9](http://dx.doi.org/10.1016/S0260-8774(03)00289-9)
- [17] Aysan Y, Sahin F. First report of bacterial blight of anthurium caused by *Xanthomonas axonopodis* pv. *dieffenbachiae* in Turkey. Plant Pathol 2003;52(6):783. DOI: <http://dx.doi.org/10.1111/j.1365-3059.2003.00892.x>
- [18] Mirik M, Aysan Y, Cinar O. Copper-resistant strains of *Xanthomonas axonopodis* pv. *vesicatoria* (Doidge) Dye in the eastern Mediterranean region of Turkey. J Plant Pathol 2007;89:153-154.
- [19] Mesomo M, Silva MF, Boni G, et al. Xanthan gum produced by *Xanthomonas campestris* from cheese whey: production optimization and rheological

- characterization. *J Sci Food Agric* 2009;89(14):2440-2445. DOI: <http://dx.doi.org/10.1002/jsfa.3743>
- [20] Liakopoulou-Kyriakides M, Psomas SK, Kyriakidis DA. Xanthan gum production by *Xanthomonas campestris* w.t fermentation from chestnut extract. *Appl Biochem Biotech* 1999;82(3):175-183. DOI: <http://dx.doi.org/10.1385/ABAB:82:3:175>
- [21] Rosalam S, England R. Review of xanthan gum production from unmodified starches by *Xanthomonas campestris* sp. *Enzyme Microb Tech* 2006;39(2):197-207. DOI: <http://dx.doi.org/10.1016/j.enzmictec.2005.10.019>
- [22] Rao MA, *Rheology of fluid and semisolid foods—principles and application*. Gaithersburg: An Aspen; 1999.
- [23] Hassler RA, Doherty DH. Genetic engineering of polysaccharide structure: production of variants of xanthan gum in *Xanthomonas campestris*. *Biotechnol Progr* 1990;6(3):182-187. DOI: <http://dx.doi.org/10.1021/bp00003a003>
- [24] Lopez MJ, Moreno J, Ramos-Cormenzana A. *Xanthomonas campestris* strain selection for xanthan production from olive mill wastewaters. *Water Res* 2001;35(7):1828-1830. DOI: [http://dx.doi.org/10.1016/S0043-1354\(00\)00430-9](http://dx.doi.org/10.1016/S0043-1354(00)00430-9)
- [25] Torrestiana B, Fucikovsky L, Galindo E. Xanthan production by some *Xanthomonas* isolates. *Lett Appl Microbiol* 1990;10(2):81-83. DOI: <http://dx.doi.org/10.1111/j.1472-765X.1990.tb00270.x>
- [26] Sánchez A, Ramirez ME, Torres LG, et al. Characterization of xanthans from selected *Xanthomonas* strains cultivated under constant dissolved oxygen. *World J Microb Biot* 1997;13(4):443-451. DOI: <http://dx.doi.org/10.1023/A:1018532418417>
- [27] Rottava I, Batesini G, Silva MF, et al. Xanthan gum production and rheological behavior using different strains of *Xanthomonas* sp. *Carbohydr Polym* 2009;77(1):65-71. DOI: <http://doi.org/10.1016/j.carbpol.2008.12.001>
- [28] Borges CD, Vendruscolo CT. Xanthan synthesized by strains of *Xanthomonas campestris* pv *pruni*: Production, viscosity and chemical composition. *Biosci J* 2007; 23:67-73.
- [29] Ben Salah R, Chaari K, Besbes S, et al. Production of xanthan gum from *Xanthomonas campestris* NRRL B-1459 by fermentation of date juice palm by-products (*Phoenix dactylifera* L.). *J Food Process Eng* 2011;34(2): 457-474. DOI: <http://dx.doi.org/10.1111/j.1745-4530.2009.00369.x>
- [30] Silva MF, Fornari RCG, Mazutti MA, et al. Production and characterization of xanthan gum by *Xanthomonas campestris* using cheese whey as sole carbon source. *J Food Eng* 2009;90(1):119-123. DOI: <http://dx.doi.org/10.1016/j.jfoodeng.2008.06.010>
- [31] Casas JA, Santos VE, Garcia-Ochoa F. Xanthan gum production under several operational conditions: molecular structure and rheological properties. *Enzyme Microb Tech* 2000;26(2-4):282-291. DOI: [http://dx.doi.org/10.1016/S0141-0229\(99\)00160-X](http://dx.doi.org/10.1016/S0141-0229(99)00160-X)
- [32] Papagianni M, Psomas SK, Batsilas L, et al. Xanthan production by *Xanthomonas campestris* in batch cultures. *Process Biochem* 2001;37(1):73-80. DOI: [http://dx.doi.org/10.1016/S0032-9592\(01\)00174-1](http://dx.doi.org/10.1016/S0032-9592(01)00174-1)
- [33] Psomas SK, Liakopoulou-Kyriakides M, Kyriakidis DA. Optimization study of xanthan gum production using response surface methodology. *Biochem Eng J* 2007;35(3):273-280 DOI: <https://doi.org/10.1016/j.bej.2007.01.036>

- [34] Borges CD, de Paula RCM, Feitosa JPA, et al. The influence of thermal treatment and operational conditions on xanthan produced by *X. arboricola* pv pruni strain 106. Carbohydr Polym 2009;75(2):262-268. DOI: <http://dx.doi.org/10.1016/j.carbpol.2008.07.013>
- [35] Gilani SL, Najafpour GD, Heydarzadeh HD, et al. Kinetic models for xanthan gum production using *Xanthomonas campestris* from molasses. Chem Ind Chem Eng Q 2011;17(2):179-187. DOI: <https://doi.org/10.2298/CICEQ101030002G>
- [36] Gupte MD, Kamat MY. Isolation of wild *Xanthomonas* strains from agricultural produce, their characterization and potential related to polysaccharide production. Folia Microbiol 1997;42(6):621-628. DOI: <http://dx.doi.org/10.1007/BF02815476>
- [37] Marcotte M, Hoshahili ART, Ramaswamy HS. Rheological properties of selected hydrocolloids as a function of concentration and temperature. Food Res Int 2001;34(8):695-703. DOI: [http://dx.doi.org/10.1016/S0963-9969\(01\)00091-6](http://dx.doi.org/10.1016/S0963-9969(01)00091-6)
- [38] Carmona JA, Lucas A, Ramírez P. Nonlinear and linear viscoelastic properties of a novel type of xanthan gum with industrial applications. Rheol Acta 2015;54(11-12):993-1001. DOI: <http://dx.doi.org/10.1007/s00397-015-0888-1>
- [39] Kim C, Yoo B. Rheological properties of rice starch-xanthan gum mixtures. J Food Eng 2006;75(1):120-128. DOI: <http://dx.doi.org/10.1016/j.jfoodeng.2005.04.002>
- [40] Martínez-Padilla LP, Lopez-Araiza F, Tecante A. Steady and oscillatory shear behavior of fluid gels formed by binary mixtures of xanthan and gellan. Food Hydrocolloid 2004;18(3):471-481. DOI: <http://dx.doi.org/10.1016/j.foodhyd.2003.07.002>

Table 1. Effect of xanthan gum concentration on activation energies, Ostwald de Waele parameters and apparent viscosity of xanthan gum solutions obtained from different isolates at 20°C.

Xanthan gum conc. (%)	Strain	K (Pa s ⁿ)	n (-)	R^2	A (Pa s ⁿ)	Activation energy (kJ/mol)	R^2
0.5	<i>X. axonopodis</i> pv. <i>vesicatoria</i>	0.375a	0.546b	0.99	$9.16 \cdot 10^{-6}$ a	23.5a	0.98
	<i>X. campestris</i> DSM 19000	0.154b	0.688a	0.99	$1.98 \cdot 10^{-6}$ b	25.43a	0.99
1	<i>X. axonopodis</i> pv. <i>vesicatoria</i>	8.098a	0.178b	0.98	0.07a	6.78b	0.96
	<i>X. campestris</i> DSM 19000	1.445b	0.457a	0.98	$7.4 \cdot 10^{-5}$ b	21.25a	0.98
2	<i>X. axonopodis</i> pv. <i>vesicatoria</i>	18.619a	0.196b	0.99	0.07a	9.07a	0.97
	<i>X. campestris</i> DSM 19000	16.295b	0.236a	0.99	0.046b	10.12a	0.97

K : consistency index; n : flow behavior index; A : constant determined from the Arrhenius relationship; R^2 : determination coefficient. Different lowercase letters show differences between the columns ($P < 0.05$).

Table 2. Effect of xanthan gum concentration on G' (storage modulus), G'' (loss modulus), R^2 (determination coefficient) values of different gum solutions obtained from different strains at 20°C.

Xanthan gum conc. (%)	Strain	K'	n'	R^2	K''	n''	R^2
0.5	<i>X. axonopodis</i> pv. <i>vesicatoria</i>	$4.1 \cdot 10^{-5}$ b	2.95a	0.99	$2 \cdot 10^{-6}$ b	3.62a	0.99
	<i>X. campestris</i> DSM 19000	0.076a	1.01b	0.95	$5.24 \cdot 10^{-3}$ a	1.51b	0.97
1	<i>X. axonopodis</i> pv. <i>vesicatoria</i>	5.95a	0.39b	0.98	3.8a	0.18b	0.99
	<i>X. campestris</i> DSM 19000	0.25b	0.99a	0.99	1.4b	0.34a	0.84
2	<i>X. axonopodis</i> pv. <i>vesicatoria</i>	18.04a	0.32a	0.99	11.21a	0.211a	0.99
	<i>X. campestris</i> DSM 19000	13.32b	0.42a	0.99	10.98a	0.259a	0.99

K' and K'' : consistency index for storage and loss modulus, respectively; n' and n'' : flow behavior index for storage and loss modulus, respectively; R^2 : determination coefficient. Different lowercase letters show differences between the columns ($P < 0.05$).

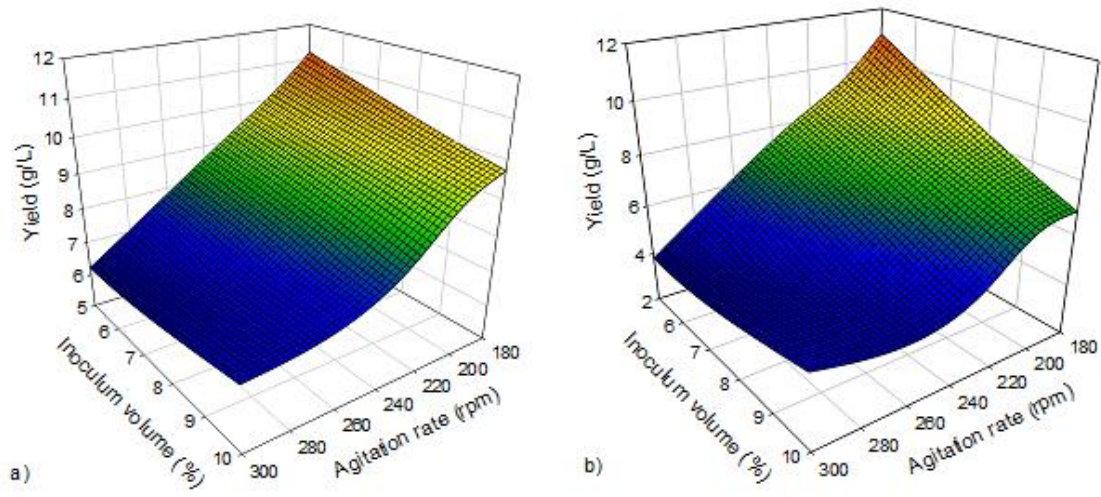


Figure 1 (a) Effects of inoculum volume and agitation rate on the production of xanthan for *X. campestris* DSM 19000 (g/L) (b) Effects of inoculum volume and agitation rate on the production of xanthan for *X. axonopodis* pv. *vesicatoria* (g/L).

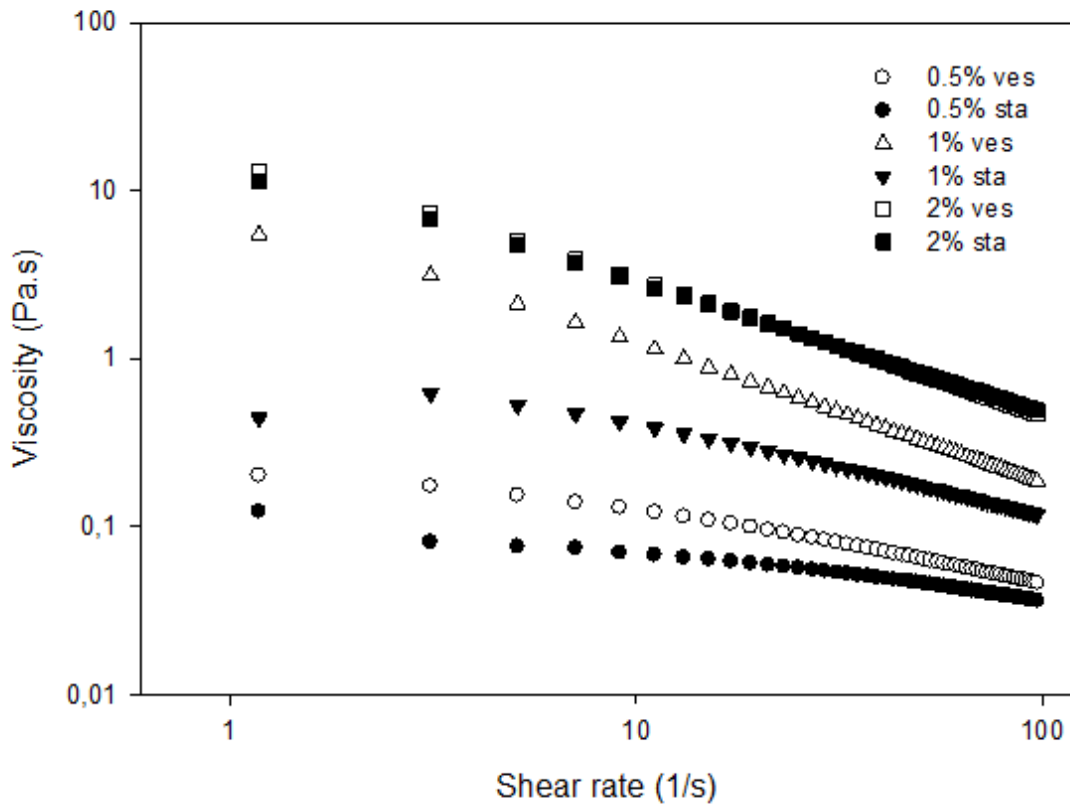


Figure 2. Viscosity change of different gum solutions against shear rate obtained from *X. axonopodis* pv. *vesicatoria* and *X. campestris* DSM 19000.

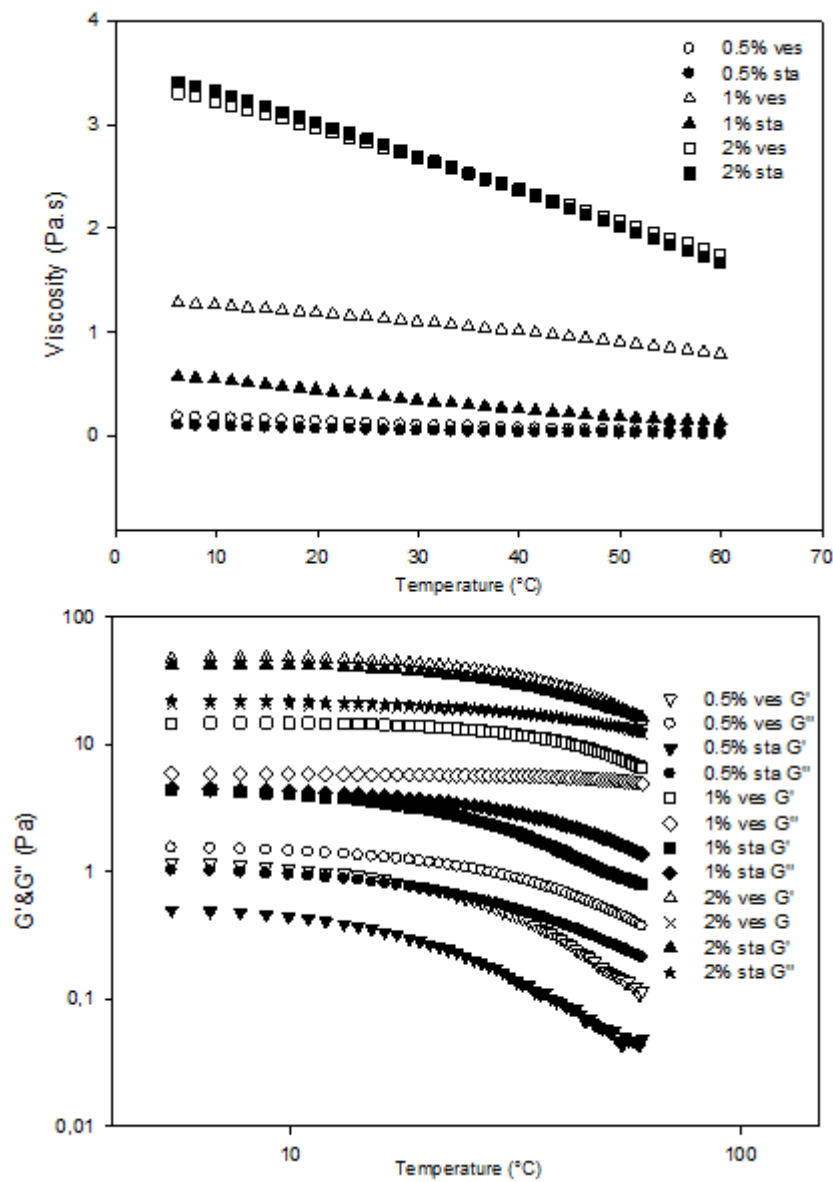


Figure 3. Viscosity, Storage (G') and Loss (G'') modulus change of different gum solutions against temperature obtained from *X. axonopodis* pv. *vesicatoria* and *X. campestris* DSM 19000.

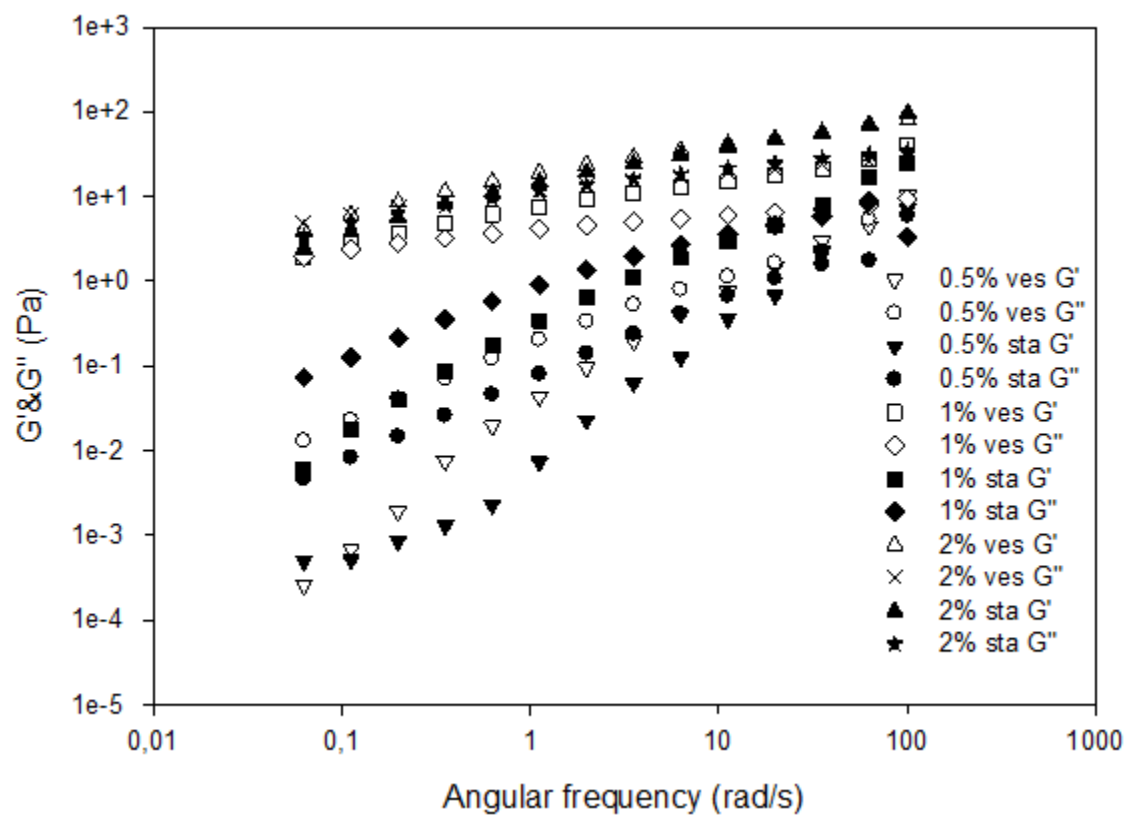


Figure 4. Storage (G') and Loss (G'') modulus change of different gum solutions against angular frequency obtained from *X. axonopodis* pv. *vesicatoria* and *X. campestris* DSM 19000.